



Article title: Moisture Buffering and Mold Growth Characteristics of Naturally Ventilated Lime Plastered Houses.

Authors: Vismaya Paralkar[1], Rashmin Damle[2]

Affiliations: Faculty of Technology, CEPT University, Ahmedabad, India[1]

Orcid ids: 0000-0003-2688-6826[1]

Contact e-mail: architectvismaya@gmail.com

License information: This is an open access article distributed under the terms of the Creative Commons Attribution License (CC BY) 4.0 <https://creativecommons.org/licenses/by/4.0/>, which permits unrestricted use, distribution and reproduction in any medium, provided the original author and source are credited.

Preprint statement: This article is a preprint and has not been peer-reviewed, under consideration and submitted to UCL Open: Environment Preprint for open peer review.

DOI: 10.14324/111.444/000135.v2

Preprint first posted online: 18 August 2022

Keywords: Lime plaster; Hygrothermal simulations; mould growth; surface relative humidity conditions., Energy and health

Moisture Buffering and Mold Growth Characteristics of Naturally Ventilated Lime Plastered Houses.

Vismaya Paralkar^a, Dr.Rashmin Damle^a

a CEPT University, Ahmedabad, India

Covering Letter

Lime plaster is one of the sustainable building materials that is also effective as a passive cooling strategy. The moisture buffering quality of lime causes adsorption and desorption of space moisture which moderates the indoor relative humidity. Its vapour permeability is influential in moisture transfer across the building envelope. Lime plaster also has a self-healing quality which prevents the formation of inner cracks. Moreover, its strength increases with time leading to a longer life span. Old historical structures standing strong for thousands of years endorse its durability. In old structures, an important function is the breathability of the ceiling and walls. Hence, it is essentially used in conservation projects and vastly adds to the appearance and durability of old buildings.

The composition of lime plaster varies from region to region. Often numerous additives are employed to impart certain qualities to the lime mortar/plaster. The presence of organic mixes and the moisture buffering quality of lime plaster make it more prone to phenomena like mold growth on the surface of the walls. Mold growth further degrades indoor air quality, and the occupant health is compromised. To avoid mold-related problems, it is necessary to understand the behaviour of lime plaster with respect to the indoor relative humidity and surface moisture content.

Several studies have reported the advantages of lime plaster and its use as a passive sustainable strategy. However, the literature lacks studies about the post-occupancy behaviour of lime-plastered buildings in terms of their indoor environment and mold growth characteristics. This information can support conservation projects to maintain longevity and improve indoor air quality. This work attempts to evaluate the state of traditional lime-plastered buildings in Ahmedabad and correlates the findings in terms of the building characteristics like coatings on the wall, ventilation, the level of water activity inside the space, the function of the space, etc. Simulations were also carried out to understand the hygrothermal performance of lime plaster. Finally, experiments were carried out to study the onset of mold growth in lime plaster samples.

Point-in-time surveys of the studied spaces showed that lime plaster could effectively modulate indoor relative humidity. Mold growth was observed in spaces that lacked sunlight and ventilation. Non-porous coatings on lime-plastered walls also led to mold growth by trapping moisture. Mold growth can be avoided by providing ventilation and allowing the lime-plastered wall to breathe. The study, therefore, explores the possibility of reviving lime plaster as a sustainable and recyclable material in contemporary construction practices.

Moisture Buffering and Mold Growth Characteristics of Naturally Ventilated Lime Plastered Houses.

Vismaya Paralkar^a, Dr.Rashmin Damle^a

a CEPT University, Ahmedabad, India

Abstract

Lime plaster is well known for its moisture-buffering capabilities but is also susceptible to mold growth. This work focuses on the hygrothermal performance of lime plaster in naturally ventilated residential spaces. Surveys are carried out for 45 traditional buildings of Ahmedabad in India with measurements of ambient variables, such as temperature, relative humidity, wall moisture content, etc. The Mold growth patterns of these spaces are related to the measured variables and wall characteristics. Hygrothermal simulations of some spaces are also carried out to observe the moisture buffering of lime plaster. Experimental observations have been contrasted with numerical simulation results to see if the numerical predictions of the hygrothermal models are realistic.

Keywords: Lime plaster; Hygrothermal simulations; mold growth; surface relative humidity conditions.

Nomenclature

T_a – Ambient Temperature inside a space.

T_o – Outside Dry Bulb Temperature.

GT_o – Outside Globe Temperature.

GT_i - Inside Globe Temperature.

μ - Moisture Content of the walls.

RH_o – Outside Relative Humidity.

RH_i – Inside Relative Humidity.

T_{s_o} – Outside Surface Temperature.

T_{s_i} - Inside Surface Temperature.

RH_s – Inside Surface Relative Humidity

v_a – air velocity at the level of the globe thermometer.

MRT_o – Outside Mean Radiant Temperature.

MRT_i – Inside Mean Radiant Temperature.

EMPD – Effective Moisture Penetration Depth

HAMT – Heat and Moisture Transport

MBV – Moisture Buffering Value

1 Introduction

The relative humidity of air in a building determines its energy performance, comfort, and indoor air quality (1). Moisture buffering characteristics of wall materials can modulate indoor humidity by absorbing/desorbing the moisture present in the indoor air. The use of hygroscopic materials in the envelope and a well-controlled HVAC system reduced the cooling and heating energy consumption by 5% and 30 % respectively (2). (3) achieved energy efficiency in buildings by combining moisture buffering with relative humidity-sensitive ventilation. By employing hygroscopic gypsum and wood fibre materials, the energy saving potential of 25 – 30 % for temperate and semi-arid climates was observed by (4). The hygroscopic interaction between the wall surface and room air affected the air temperature by 2 to 3 °C (5). Due to moisture buffering, up to 20 % reduction in heating energy was observed in different climate zones of India (6).

Apart from the energy aspect, relative humidity also affects the concentration of noxious gases in the air as it alters the rate of off-gassing in the building materials. Due to microbial interactions, odorous and irritant substances or allergens are emitted from damp materials. The presence of moisture is a cause of deterioration inside buildings (7) while affecting the latent and sensible conduction loads (8). Relative humidity coupled with high temperature has adverse effects (direct as well as indirect) on human health leading to allergic incidences and respiratory diseases (9). Several health issues like asthma and respiratory disorders are associated with the dampness in buildings.

The fungal growth on building surfaces is highly influenced by the relative humidity of indoor air. 21 different types of building materials were studied (10) to understand the influence of temperature and relative humidity on the metabolism and growth of eight different micro-fungi. Under constant temperature conditions, with relative humidity up to 95% and water activity at 0.95, *Penicillium*, *Aspergillus*, and *Eurotium* overgrew other indoor fungi. The minimum water activity for fungal growth in materials susceptible to mold growth is 0.78 – 0.8. For the same water activity, favourable conditions for mold occur at 10°C under 80 – 90% relative humidity and at 5°C for relative humidity more than 90%. The four sources of dampness and moisture in the building are leakage of rain and snow into the building construction or moisture from the ground; moisture from occupants and their indoor activities; water leakage (11). The moisture starts accumulating if the rate at which moisture enters an assembly exceeds the rate of moisture removal (12). Moreover, the problem of even small water leaks has a significant impact if the moisture buffering capacity of the material is low. Therefore, the moisture transfer/buffering capacity of building materials plays a vital role in regulating the indoor relative humidity by moisture transfer through the building envelope.

Lime is an environment-friendly material that has been forgotten in contemporary construction practices. Before the advent of Portland cement lime mortar and lime plaster were widely used as binder and finishing materials. The use of lime plaster in the caves of Ellora (13) and baked brick walls at Karvan (14) in India date back to the 6th century AD. Lime plaster mixed with hemp, dolomite, or cannabis was applied in different layers for longevity (15). Lime has lower embodied energy (16) and excellent moisture buffering capacity. (17) reported a reduction in humidification and dehumidification energy requirements with lime-stabilized bentonite clay. In comparison to cement mortars, lime-based mortars had three times more moisture buffering capacity (18). Post occupancy analysis of lime-plastered spaces in a warm & humid climate zone showed 7.3 % lower indoor humidity levels (1). Lime plaster is also vapor-permeable i.e., useful in ‘breathing wall’ construction (19). Its strength increases with time and remediation of cracks and defects is easy. It is recyclable, involves nontoxic chemicals for manufacturing, and its production can be downscaled as per need. When used as an internal render, it improves indoor air quality by absorbing low amounts of carbon dioxide and regulating indoor relative humidity for a prolonged period. Lime avoids problems of decay and dampness by allowing the building envelope to breathe and unlike several modern nonporous materials (20). It is highly influential in the moisture transfer of a building envelope. Lime plaster is less rigid and brittle than cement plaster. Lime

mortar and lime plaster are self-healing through the autogenous process of evaporation of penetrated water which prevents the formation of inner cracks. A study by Apte (21) suggests that developing India should utilize freshly ground lime against cement. The use of incompatible materials like cement plaster or chemical paint on walls causes deterioration of the building envelope in heritage structures (22). It traps the moisture inside and soon the walls crumble and fall off (23). For conservation projects, lime is a good repair material for preserving the architectural heritage (24).

One of the issues with lime plaster is mold growth which leads to poor air quality. The rain exposure impact is low on hygrothermal performance of a capillary closed material like mineral plaster. But the impact is significant on mold index for a lime plaster assembly (25). Material like lime plaster has higher capillary action and its moisture content is vastly dependent on its exposure to driving rain (26). The presence of moisture in or on the surface of walls invites a favourable atmosphere for mold growth (27).

Variations in the location of humidity sources and room ventilation rates give rise to pockets of high relative humidity. Therefore, the average relative humidity throughout the building should be maintained between 40 % to 60 %. It was observed that all types of building materials are prone to mold growth above 15 °C and 90 % RH (28). For over a year no fungal growth is noticed for a lower RH of 80%. One of the techniques for limiting mold growth in most of the large buildings in the US is building pressurization. A study (29) suggests that for spaces modelled in a hot and humid climate, the effective solution is positive pressurization and keeping a higher setpoint of indoor temperature. Another way is to increase the amount of pozzolana in a lime plaster mixture. Pozzolana reduces the water vapour diffusion resistance (27) and thus increases moisture transfer across the building envelope.

It is clear from the literature that lime mortar/plaster has numerous advantages. However, due to its moisture absorbing capacity and use of organic additives, it is hugely prone to issues of mold growth. The composition of lime plaster varies from region to region. There is literary evidence (30) linking to the composition of lime mortars used in India. It can be stated that they included ingredients like curd, jaggery, Bel pulp (from the fruit Aegel marmelos), lentils, and the oil of Margosa. These mixes were used for obtaining different properties of the lime mortar. The presence of such organic mixes and moisture buffering quality of lime plaster makes it more prone to phenomena like mold growth on the surface of the walls. This degrades the indoor air quality and the occupant health is compromised. Therefore, to prevent mold growth it is necessary to understand the behaviour of lime plaster with respect to the indoor relative humidity and surface moisture content. It is also necessary to understand the causes and conditions favourable for mold growth and explore controllable parameters to avoid it. The literature lacks information about the post-occupant behaviour of lime-plastered buildings in terms of their indoor environment and mold growth characteristics. This information can be very useful for conservation projects for maintaining longevity and improving indoor air quality.

The main objective of this work is to study naturally ventilated lime-plastered spaces and correlate the observed mold growth in terms of the building characteristics like coatings on the wall, ventilation, the level of water activity inside the space, and the function of the space, etc. Secondly, hygrothermal simulations are carried out to assess the capability of the EMPD (Effective Moisture Penetration Depth) model (30) to capture moisture buffering in lime plaster. Finally, experiments are also carried out to study the onset of mold growth in lime plaster samples kept at different relative humidity levels.

2 Methodology

The research methodology adopted in this work consists of the following three parts:

1. Survey of Naturally Ventilated Residential Spaces
2. Simulating the studied spaces with an Effective Moisture Penetration Depth (EMPD) Model using Energy Plus (31).
3. Study the onset of mold growth in lime plaster samples

The cumulative inferences from the above were used to correlate the overall hygrothermal performance of lime-plastered spaces and the onset of mold growth. Furthermore, the factors leading to mold growth were also identified. Lastly, the capability of the EMPD model to predict hygrothermal performance was verified by carrying out annual simulations and contrasting the simulation results with those observed onsite.

Survey of naturally ventilated residential spaces

Two different types of naturally ventilated lime-plastered houses were surveyed in the city of Ahmedabad. Ahmedabad falls in the hot-dry climate zone of India. The heritage city of Ahmedabad includes thousands of Pols, a dense cluster of residences belonging to people of the same caste, religion, and occupation. For more than 300 years, these neighbourhoods are popularly known as Pol houses. The passive strategies in the design of Pols are prominent. Strategies protecting the inside spaces from direct heat gains include mutual shading, thick walls, long shared walls, central courtyard, multi-story structure, narrow lanes, dense clusters, etc. (32). The ota (plinth) outside the house is usually used to dry clothes in some houses. Attached to the ota (plinth) is a small, dedicated space for washing utensils and toilets. The construction of the house is of timber, brick, and lime plaster.

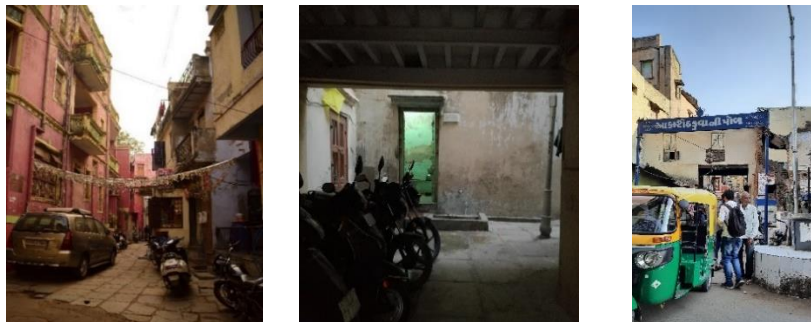


Figure 1 Pol Houses

Detached lime-plastered residences were also studied and are shown in Figure 2. Girikunj Residence (Figure 2a) is a residential bungalow (33), designed using passive design strategies and traditional materials and methods. The ventilation system is well designed using glass exhaust shafts on the periphery. These shafts collect hot air from the small grill outlets in the spaces when the windows are closed. Air vents attached to it exhaust this air to the outside. Lime is employed for plastering, wall wash, and mortar. It consists of additives like Gur (jaggery), Gugal (Indian bdellium), and Methi (fenugreek) for improving binding and waterproofing.

The RSR Residence (Figure 2b), a bungalow designed by Abhikram Architects (40), is constructed using lime mortar and lime plaster. The type of lime plaster used is Marmarino lime plaster which gives a marble-like finish. The walls were not coated with paint. Mechanical ventilation is provided with the help of exhaust fans and air vents throughout the space.



Figure 2 (a) Girikunj Residence (Source: Abhikram Architects); (b) RSR Residence

The surveys were carried out in the afternoon from 2:00 pm to 4:00 pm when the outdoor temperatures were relatively high. Measurements were taken on every alternate day from the 25th of December 2019 to 16th March 2020. A layout of the space was created considering the wall thickness, opening area, and adjacent spaces. The use and activities of the space were also noted.

Point in time measurements (Figure 3) of the outdoor air temperature, relative humidity, globe temperature, and air velocity were noted for each space. Similarly, inside air temperature, relative humidity, globe temperature, and air velocity at the center of the space were measured. For measuring the inside surface temperatures of all the walls, the emissivity of the FLIR thermal Gun was set to 0.95. The surface temperature of the ceiling and floor was also noted.

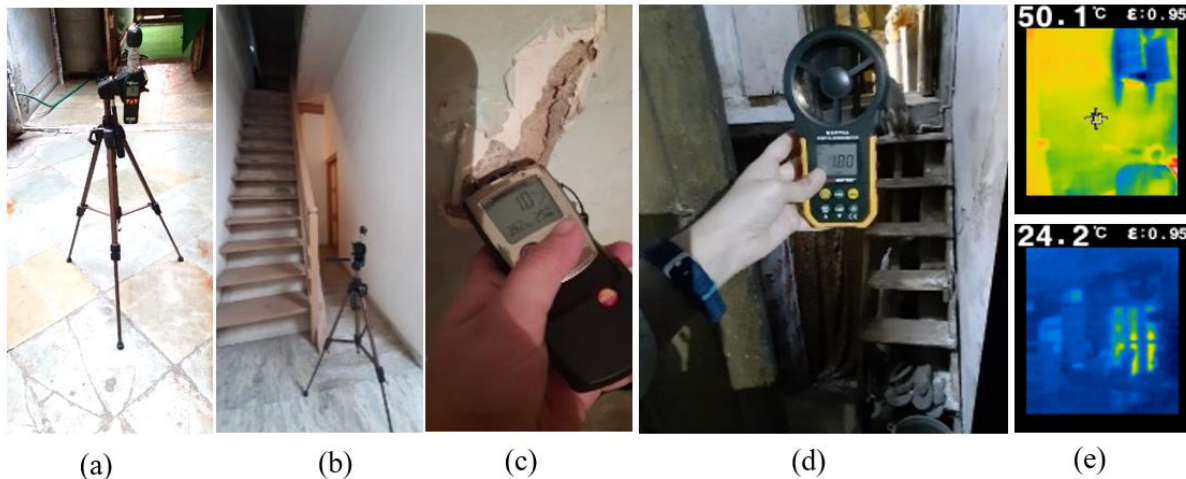


Figure 3 Site Measurements using several instruments

The details of the instruments employed for measurements in Figure 3 are the following:

- (a) Outdoor Air, RH, and Globe temperature using EXTECH Heat Stress meter,
- (b) Indoor Air, RH, and Globe temperature using EXTECH Heat Stress meter
- (c) The Moisture Meter reading of exposed lime plaster (TESTO Moisture Meter: 606-2),
- (d) Air velocity reading using Vane Anemometer (PEAKMETER MS6252A) and
- (e) Surface temperature readings of external and indoor walls using Thermal Gun (FLIR: TG165).

Table 1 gives the details of the measured parameters, their location, and the respective instruments.

Table 1 List of instruments and their measured parameters

Instrument used	Parameter measured	Measurement location
Heat Stress WBGT Meter (Extech HT30)	Outside air temperature, relative humidity, Black Globe Temperature	Outside the survey space at a height of 1100 mm from the ground
Heat Stress WBGT Meter (Extech HT30)	Inside air temperature, relative humidity, Black Globe Temperature	At the center of the survey space at a height of 1100 mm from the FFL.
Vane Anemometer (PEAKMETER MS6252A).	Air velocity	1. Near the globe thermometer, perpendicular to three planer axes. 2. Perpendicular to the vertical plane of the openings inside a space.
Thermal Gun (FLIR TG165)	Surface temperature.	Inside and outside exposed surfaces of all the walls surrounding the space (including the ceiling and floor).
Testo 606-2 Moisture Meter (38767439/711)	Moisture Content and surface relative humidity.	Moisture content inside lime plaster and surface relative humidity near it.

Forty-five spaces were surveyed in Pols which had lime plaster as the rendering material with characteristics mentioned in Appendix

. The volume is calculated from the measurements taken for floor plans.

Simulating the studied spaces with the EMPD model.

Before simulating the surveyed spaces, preliminary simulations are worked out with the Building Energy Simulation Test (BESTEST) geometry (34). These simulations are carried out with both the EMPD (Effective Moisture Penetration Depth) (35) and thermal-only i.e. the conduction transfer function (CTF) models of Energy Plus (31). The EMPD model considers the moisture absorption and desorption at wall surfaces, while the thermal-only model ignores it completely. The purpose of employing these two models is to check whether moisture absorption and desorption at the wall surfaces are captured by the EMPD model. Several authors (4,35–37) have employed the BESTEST geometry in their hygrothermal studies. Figure 4 shows the BESTEST geometry which is a single-zone space of 8m x 6m x 2.7m. The space has a moisture source of 500 g/h from 9 a.m. to 5 p.m. and a constant air change rate of 0.5 air changes per hour for Ahmedabad weather. The walls are assumed to be made of brick walls. For the inner wall surfaces finishing materials such as gypsum plasterboard, plywood, and lime plaster are considered.

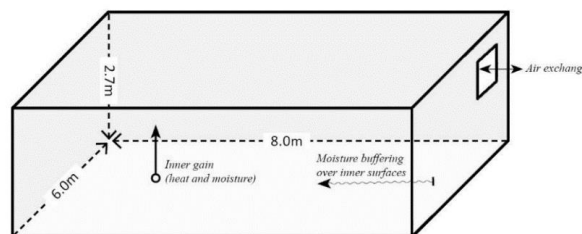


Figure 4 BESTEST Geometry (Source: (34))

EMPD is a simplified model which considers the moisture absorption and desorption at wall surfaces. It assumes a thin layer of air near the wall surface which is dynamic and exchanges moisture in the air in cyclic pulses of air moisture. EMPD gives a reasonable approximation of reality for short periods

when there is no net moisture storage (38). EMPD model is employed in this work because it needs lesser information on hygric properties of materials in comparison to the detailed HAMT (Combined Heat and Moisture Transfer) model of EnergyPlus (31).

It is a challenge to derive a universal sorption curve for lime plaster as its composition is site-specific and varies from region to region. The sorption curve was derived from the moisture content values of building materials available in the literature (39). The sorption coefficients were then derived through these moisture content values by a close-fitting curve as shown in Figure 5. The difference observed between the curves is very minuscule with a maximum difference of $0.002 \mu(\text{kg}/\text{kg})$. These values were then fed into the EMPD model to carry out simulations. After carrying out hygrothermal simulations for BESTEST geometry, a sample surveyed space is simulated with the EMPD model. The change in mean radiant temperature (MRT), relative humidity, and surface temperatures were observed through simulations. This further helped to predict the trend of the hygrothermal behaviour of lime plaster in that space throughout the year. The weather files for simulation are taken from Energy Plus weather data. ([Ahmedabad weather data](#)).

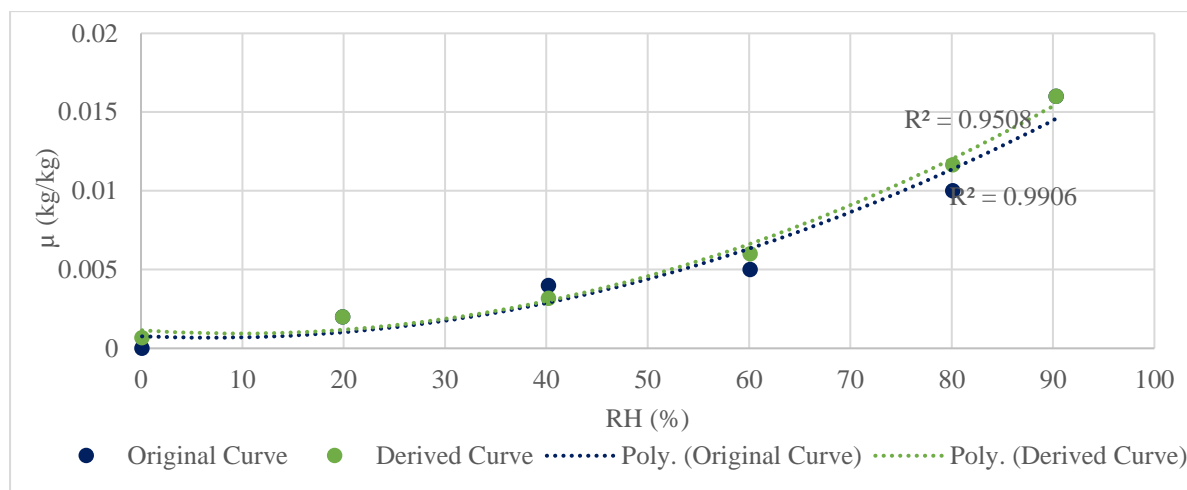


Figure 5 Best-fit sorption curve for lime plaster

Studying the onset of mold growth in lime plaster samples

To understand the onset of mold growth on lime plaster, an experiment similar to (40) was carried out. Different relative humidity levels were maintained in containers by different salt solutions. For this experiment, four plastic containers were filled with different salt solutions as shown in Figure 6. Table 2 shows the different salts and the quantity of salt and water to maintain the RH level inside the container. Preliminary trials were carried out by trial and error to fix the amount of salt and water to obtain the specific RH value. The temperature and relative humidity loggers (Hobo U10) were attached on the inner side of the lid of the jars to ensure constant relative humidity inside the containers.

Table 2 Relative humidity achieved for different Salt compositions

Name of Salt	Composition of Salts	RH Gained	Quantity (g)	Water Quantity (g)
Sodium Chloride	NaCl	75%	53.33	27.283
Ammonium sulphate	$(\text{NH}_4)_2\text{SO}_4$	80%	53.33	30
Potassium Chloride	KCl	86%	30	10
Potassium sulphate	K_2SO_4	99%	53.33	18.19



Figure 7 Lime plaster samples used for experiment Figure 6 Jars containing different salt solutions

The samples of lime plaster (see Figure 7) contained one part of lime putty, one and a half parts Surkhi (red brick powder), and two parts of sand in the mixture. Additives such as jaggery water and Gugal (Indian bdellium) water were also mixed. Using Hobo loggers (U10 Temperature and humidity loggers), the relative humidity was logged for four weeks to check the relative humidity levels inside. Once the desired RH levels were achieved, lime plasters samples of equal size (40mm x 40 mm x 10 mm), weight, and composition were introduced into the containers. These samples were left unattended until the visible mold was observed on the surface.

3 Results and Discussions

3.1 Simulation results with the BESTEST geometry

Figure 8 shows the relative humidity (RH) in the space with lime plaster as the finish material for inside surfaces. The contrast in the RH levels of thermal-only (CTF) and EMPD models is visible. In the case of the CTF model, the RH levels go up to 100%. While with the EMPD model, the RH levels are maintained between 39% to 95%. Thus, the EMPD model (31) captures the moisture buffering effect of lime-plastered wall surfaces.

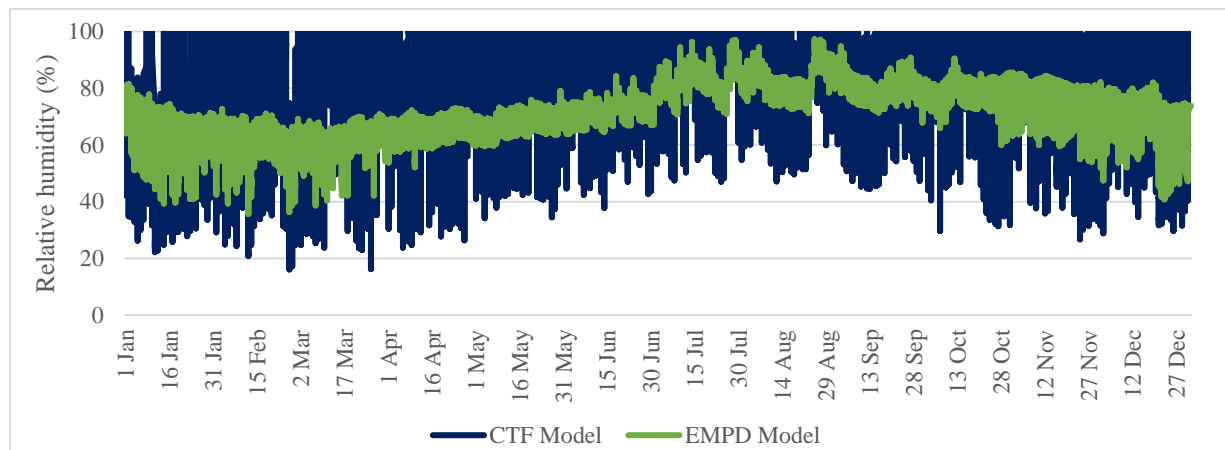


Figure 8 Relative Humidity of space with CTF and EMPD Models

Simulations with the EMPD were also carried out with gypsum plasterboard, and plywood as inner surface finishes. Figure 9 shows the box plot of RH values for the different cases. Amongst the different surface finish materials, lime plaster showed the least variation in RH levels and the least amplitude. In cases of gypsum plasterboard, plywood, and no plaster material the maximum RH is 99%. While the maximum RH with lime plaster was about 97%. RH values with lime plaster and plasterboard don't drop below 30% for the given conditions. Also, 50% of the time RH with lime plaster was in the range of 62% to 72%. The RH values were lower during moisture increase and higher during moisture

reduction with lime plaster. The above confirms the better performance of lime plaster over the rest of the finish materials.

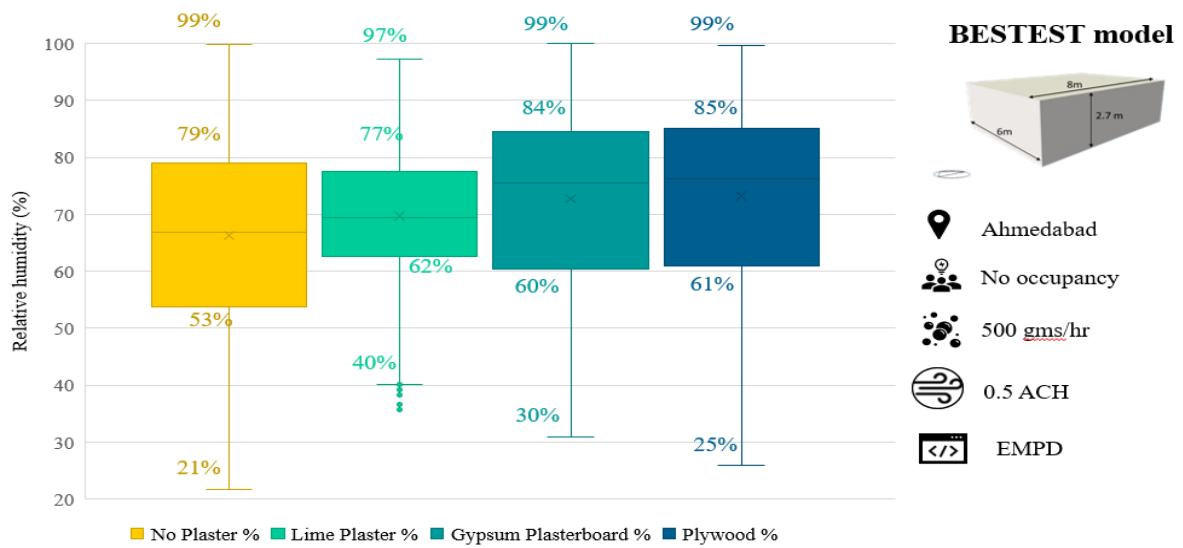


Figure 9 Indoor relative humidity in different materials

3.1.1 Simulation Results of Survey Sample Space

To observe the hygrothermal performance under actual circumstances, two spaces from the surveyed sample were modelled. The performance in terms of MRT and indoor RH was observed throughout the year. Two spaces PT_B and PS_A where mold growth was observed during the survey were selected for simulation. Physical parameters similar to the actual case were created except for the lime composition as it was unknown for the actual case. In both cases, there was no external source of the moisture other than all-time occupancy (occupancy number is as per observations on site).

Figure 10 shows the temperature variations observed from outdoor to indoor throughout the year for space PT_B. The outside DBT varied with a maximum diurnal variation of 20°C and a minimum variation of 7°C. The indoor air temperature variation is around 5°C. Similarly, the variation of the MRT inside the space was around 2°C and was maintained between 20 to 30°C for this space.

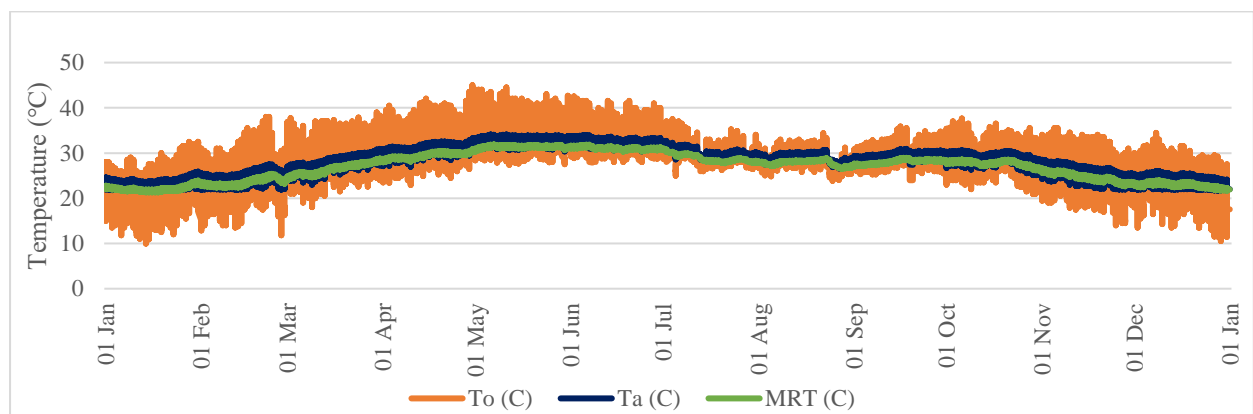


Figure 10 Outdoor, indoor, and mean radiant temperature in space PT_B

The outdoor RH levels were compared with indoor and surface RH levels in Figure 11. The outdoor maximum was 11.5 units higher than the indoor maximum and the outdoor minimum was 11 units lower than the indoor minimum. Also, the difference between the first quartile and third quartile was 33% for outdoor RH and 24% for indoor RH. It was observed that the surface RH levels were higher than the indoor RH levels. The RHs maximum was higher by 3 units while the RHs minimum was

higher by 7 units when compared to the maximum and minimum values of RH_i. To prevent mold growth, ASHRAE suggests that it is necessary to keep the spaces below 60% RH (41). However, 25% of the surface RH values were more than 70% leading to mold risk.

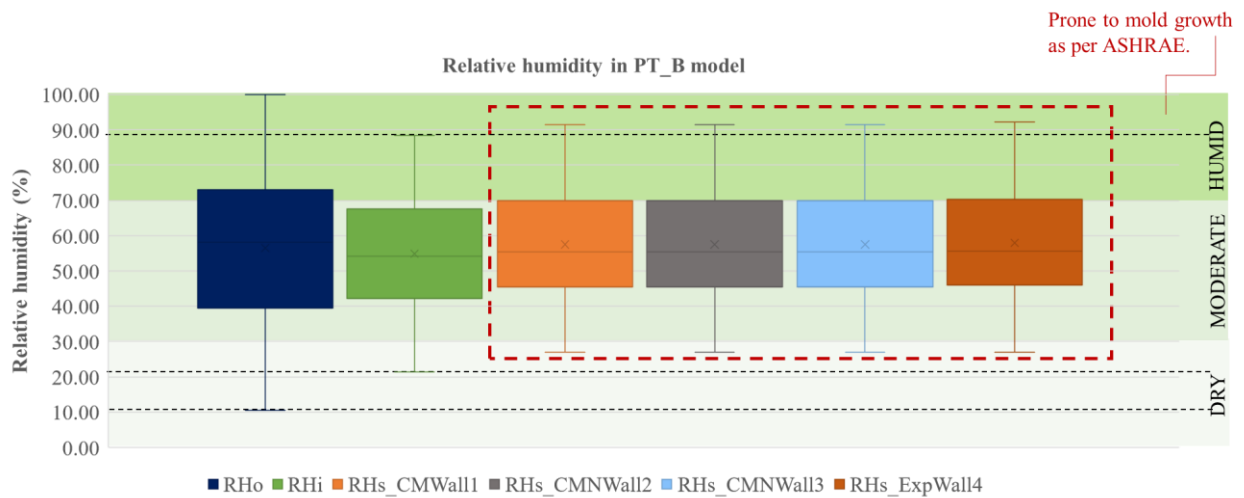


Figure 11 Indoor and surface relative humidity levels in PT_B

Figure 12 indicates varying RH levels over the year. During the monsoon months (from July – October), the indoor RH was always above 60%. While the surface RH of the walls was always above 68%. These are the months when the wall surfaces are highly prone to mold growth.

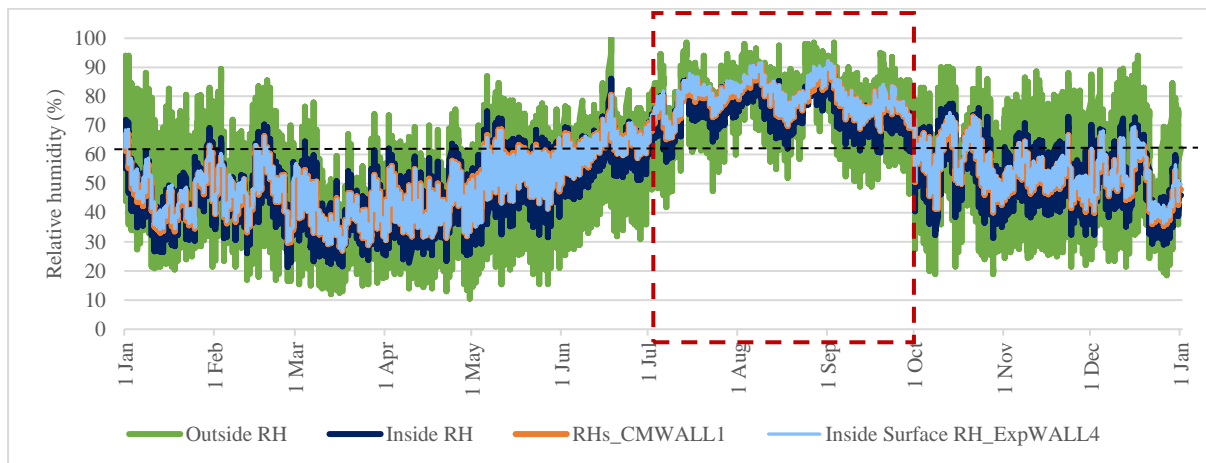


Figure 12 Relative humidity levels throughout the year in PT_B

The percentage of hours when RH levels were favourable for mold growth is shown in Figure 13. Out of 8760 hours, 32 to 54 hours were above 90% RH near the walls. 60% of the hours were between 60% - 90% RH resulting in a risk of mold growth. Even though, the simulation results show an equal percentage of high RH near the walls, the percentage of mold growth observed on-site over each wall was different. This could be because of the varied placement of furniture, openings, and air velocity adjacent to each wall.

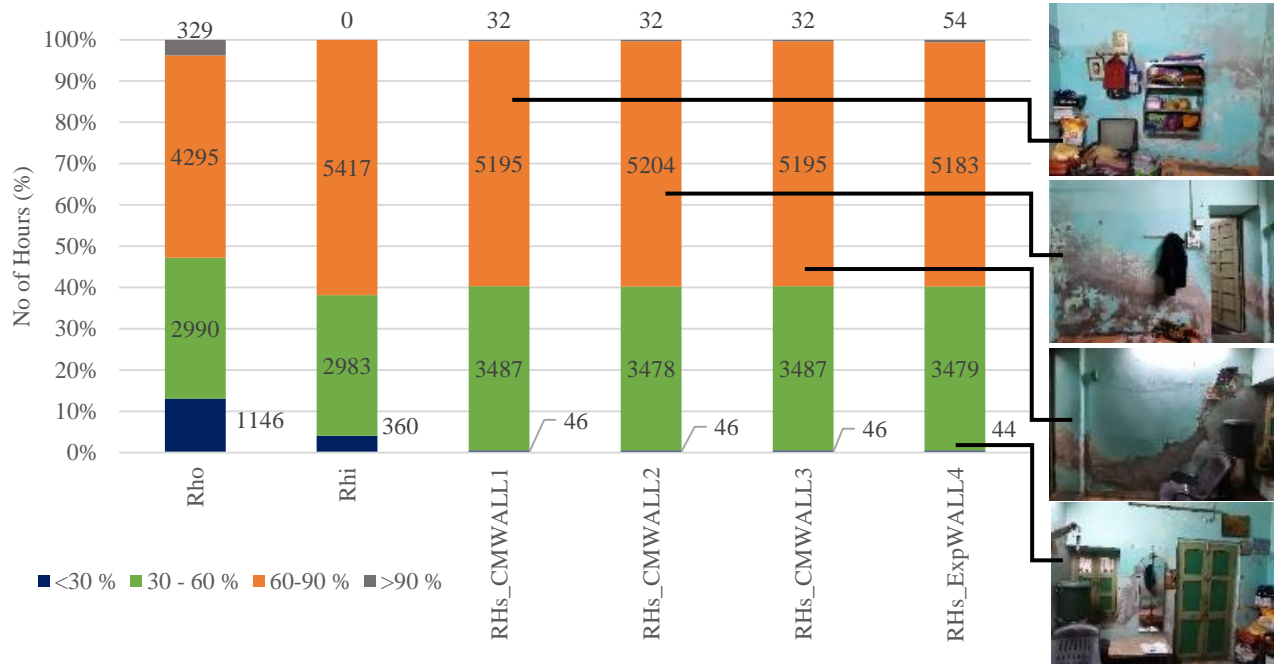


Figure 13 Hours corresponding to relative humidity ranges over the year

The space PS_A had an occupancy of 3 and showed mold on all the walls as in space PT_B. Plots similar to PS_B are not included to avoid repetition. The percentage of mold observed in PT_A was less as compared to PT_B. The simulation results also support the same. In this case, the indoor RH maximum was lower than the outdoor maximum RH by 17 units, and the maximum surface RH values were below 90 %. The surface RH near the walls varied from 60% to 80% in the monsoon months (July- October). This period is favourable for mold growth. Through simulations of spaces PS_B and PS_A, the moisture buffering and indoor MRT were observed. The indoor RH was moderated, and the MRT was lower in these spaces. Lime-plastered spaces maintain MRT between 20°C to 30°C. The indoor RH levels were lower than the outdoor RH by 9 -11 units. Overall, simulations helped to predict the duration for which the walls would be exposed to high RH levels (>70 %) that lead to mold growth.

3.2 Survey Results:

The observations from the surveyed Pol houses and residences are discussed in this section. The spot measurements sample is about 85-90 readings for each space during the study span from 25th December 2020 to 16th March 2020.

3.2.1 Pol Houses

The surveyed Pol houses were categorized according to the coatings used over lime plaster. During the study period (December to March) the RH levels varied between 10 % - 55 %. The indoor minimum values of RH were higher by 2.1 and 1 units in the case of lime-washed and non-porous painted walls. Slightly higher indoor RH levels could be due to indoor occupancy and moisture generation. To further examine the simulation observations for sample space PT_B, the onsite readings were analyzed. In Figure 14, the outdoor relative humidity is compared with the indoor and surface RH levels from January to March.

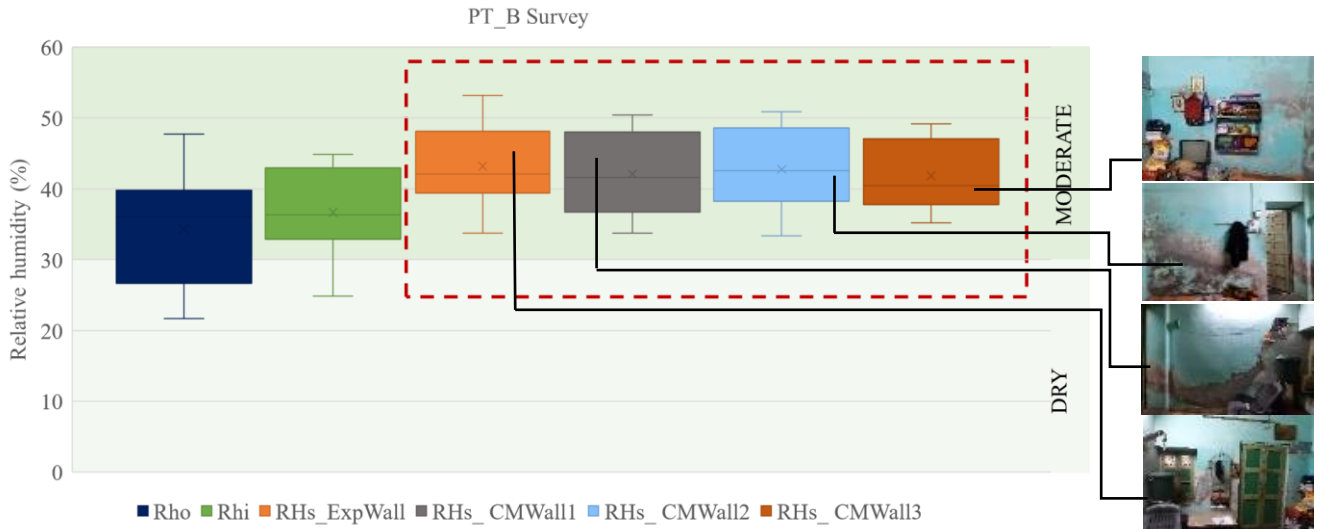


Figure 14 Onsite relative humidity levels inside PT_B

Similar to the simulation results (refer Figure 11), surface RH levels were higher than the indoor RH levels. 50% of the indoor readings were higher than outdoor indicating a humid indoor environment. The minimum values of surface RH were 9.8 to 12.4 units higher than the minimum indoor RH. The maximum surface RH is 4.3 to 8.3 units higher than the maximum indoor RH. If the above pattern is followed throughout the year, whenever the space RH goes above 60%, the surface RH will be around 65 to 70 % RH. In the monsoon period, when the outside RH levels are in the range of 80-95%, the surface RH of the walls could reach 95 to 97%. These RH levels are favourable for mold growth unless the moisture is removed from the surface.

3.2.2 Girikunj Residence and RSR Residence

For Girikunj Residence, the surveyed spaces included a basement and topmost rooms exposed to the sun. Figure 15a shows the relative humidity in the study period of March. The outdoor RH near Girikunj varied between 14.6% to 40%. The RH in indoor spaces varied between 18.2% to 37.4%. A difference of 3% to 4% was observed between the high and low values from outdoor to indoor. No water activity or occupancy (excluding the surveyor) was observed inside any of these spaces.

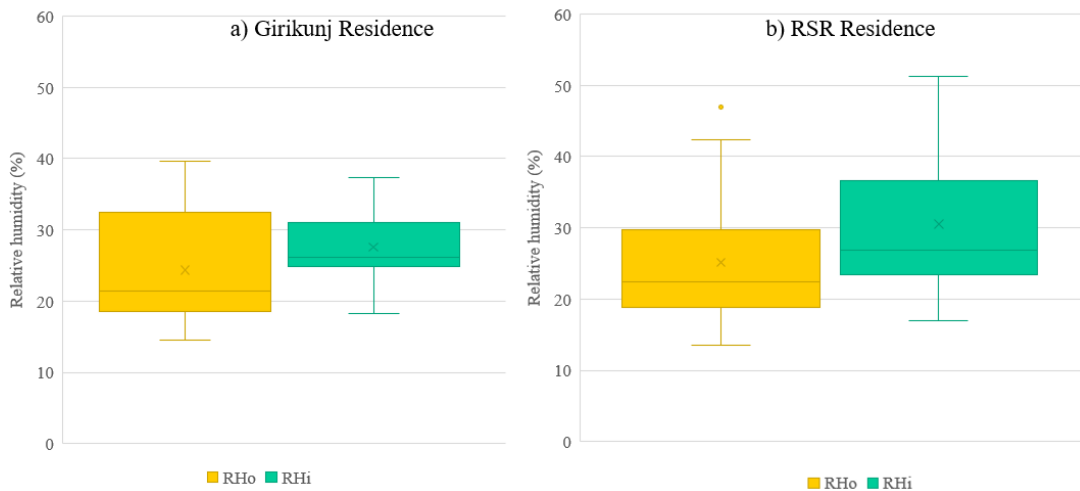


Figure 15 Indoor relative humidity of different spaces

The topmost coating in RSR residence is that of Venetian lime plaster which is a smooth marble-like lime plaster that doesn't require any paint. Thirteen spaces on the ground floor were surveyed in the

month of March. Figure 15b shows the indoor and outdoor RH levels. The mean of indoor RH was higher than that of outdoor by 4.7%. Mold growth was observed in one of the spaces (RJ_K). In this space, the indoor RH was higher by 8 to 14 units and a maximum difference of 18 units was observed between the surface RH and indoor RH. An adjacent space, RJ_J, was found to be free of mold. The indoor RH in RJ_J space was higher by 1 to 5 units while the surface RH was higher than indoor RH by 5 to 9 %. Thus, the correlation between higher surface RH and mold growth was observed through on-site surveys.

3.2.3 MRT observations

Figure 16 shows the difference between outdoor and indoor MRT for all the studied spaces. The MRT of space was calculated as per the formula given in (42). With increasing outdoor temperatures, the difference increases for all the spaces except those having a nonporous coating over lime plaster. A positive difference shows that the indoor MRT is lower than the outdoor MRT. The differences were highest (indicated by a steeper trendline) for RSR residence where lime plaster was exposed. The differences for Girikunj were lower than RSR residence and least for Pol houses with limewash.

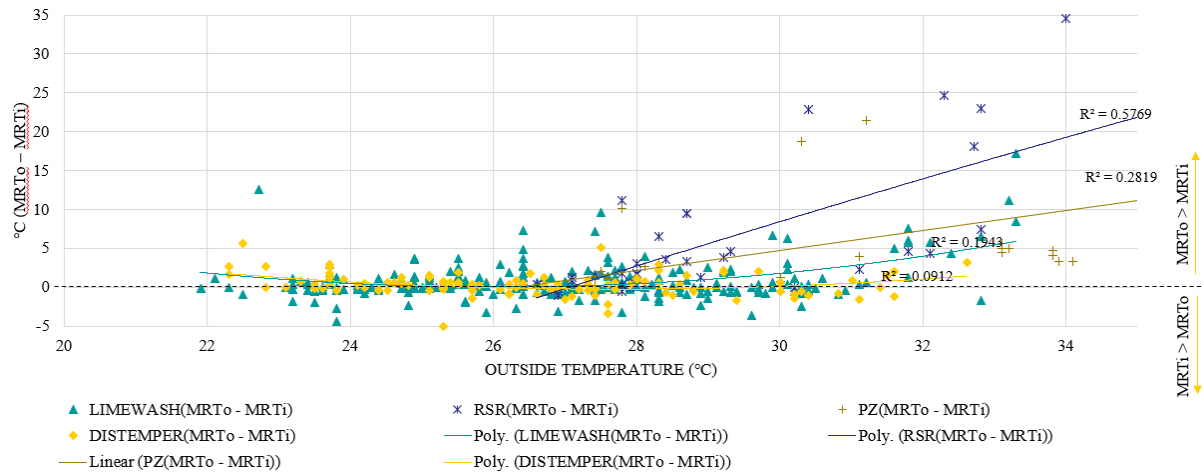


Figure 16 MRT Variation with outdoor temperature for different spaces

The indoor was considered to be comfortable when inside MRT (MRT_i) was found to be lower than the outside MRT (MRT_o). Based on above criteria, it was observed that the spaces with non-porous paint were hot 30 % of the time. Limewashed spaces in Pol houses remained hot for 18.5 %, while RSR and Girikunj residences stayed hot for 8.6 % and 7.4 % respectively. Thus, RSR and Girikunj Residences were comfortable for more than 90% of the time. Pol houses with limewash were comfortable for 81% of the time in March. These differences could be more in hotter months and need to be studied further by year around measurements.

3.2.4 Mold Risk Observations

From the surveys, it was observed that the hygrothermal behaviour of spaces varied with their characteristics. The spaces were identified based on the topmost finish of the wall surface layer, air velocity inside the space, occupancy, storage, the sunlight received and the type of activity happening in that space. Figure 17 shows photos of different spaces with visible mold growth.



Figure 17 Onsite photos of different locations with mold growth.

For further analysis, the moisture content of the walls was recorded and is shown in Figure 18. The walls of the spaces where mold growth is observed are marked in orange. During the study period from December to March, all the walls were dry and showed low moisture content below 2%. However, mold growth was still observed on these walls. The mold would have grown during the past monsoon season from July-October when the RH levels were in excess of 90 % for sustained periods. Factors like damaged construction, presence of water pipelines, low ventilation, etc., were other reasons for mold.

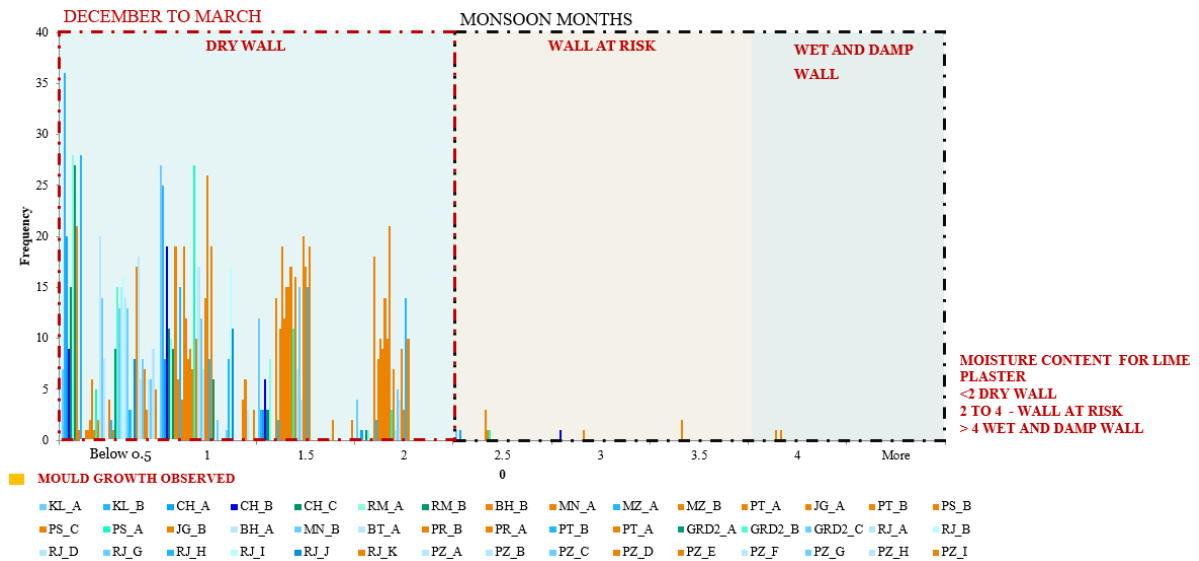


Figure 18 Moisture content of all walls surveyed between December 2019 and March 2020

Since the study was conducted in drier months there were hardly any walls having a moisture content of more than 2%. Nonetheless, mold was present on these walls which can further be analyzed by understanding the correlation of moisture content with the surface relative humidity. In Figure 19, the wall moisture content is plotted against the indoor surface relative humidity. The points marked in orange, ochre, red, and maroon represent the readings of walls having mold. The rest of the points are shown in blue colour. The graph is divided into six sections by referring to the characteristic curve of lime mortar in the moisture meter (43). For surface humidity above 60% and moisture content above

2%, there are definite chances of mold. For relative humidity below 30% and 1.5 moisture content, the conditions are dry enough to restrict mold. Walls with mold showed moisture content greater than 0.5%.

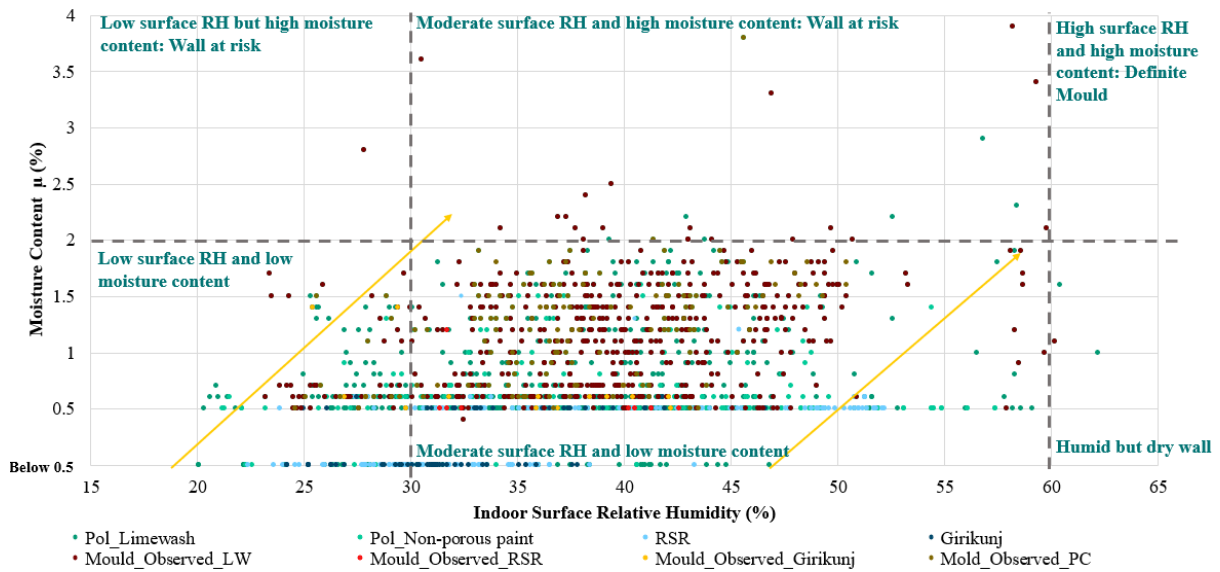


Figure 19 Moisture Content vs surface relative humidity

In case of Pol houses, most of the readings in Figure 19 are populated in the section of moderate humidity and drywall. These also include walls affected by mold due to the predated wet monsoon season. Thus, the poor performance of the building during monsoons or due to specific damage is evident. Points lying below 60% surface humidity and above 2% moisture content suggest mold growth due to the trapped moisture in the walls. Points in bright red are of RSR residence, where the reason for the presence of mold was the existence of a water pipeline and high moisture source (pool) outside the space. In Girikunj residence (marked in dark blue) the mold was observed in the basement and space attached to the terrace. Due to leakage near the slab of the terrace during rain, the walls might have been damaged. There are numerous blue points observed towards the right of the graph indicating well-ventilated and undamaged walls. Overall, a gradual shift towards the right is observed with the increase in indoor surface relative humidity. This indicates the increase in moisture content with the increase in the indoor surface relative humidity.

Figure 20 shows the mold scenario of each space with respect to its characteristics. It helps in identifying the strongest and most common factors that affect mold growth as observed and measured during the multiple site visits. The spaces highlighted in black are indicative of mold growth. All the spaces were further categorized and color-coded as per the following characteristics:

- Plaster paint: coating used over the plaster-like lime wash paint, distemper paint, plastic emulsion paint, or not coated. If the topmost coating is nonporous, the moisture is trapped inside, resulting in mold growth.
- Ventilation: if the wall surfaces are not properly ventilated, the moisture inside the pores of the finishing layer doesn't evaporate and leads to mold growth.
- Sunlight: Sunlight plays a role in killing bacteria and keeping highly humid surfaces dry.
- Water Activity: high water activity i.e., activities like washing, cleaning, etc., result in higher moisture inside the space.
- Clutter near the wall (storage): more stuffed spaces create humid pockets inside the space. Clutter is considered low, moderate, and high if the furniture and other items are blocking the walls by 30%, 60%, or 70%. This was based on just visual observations.

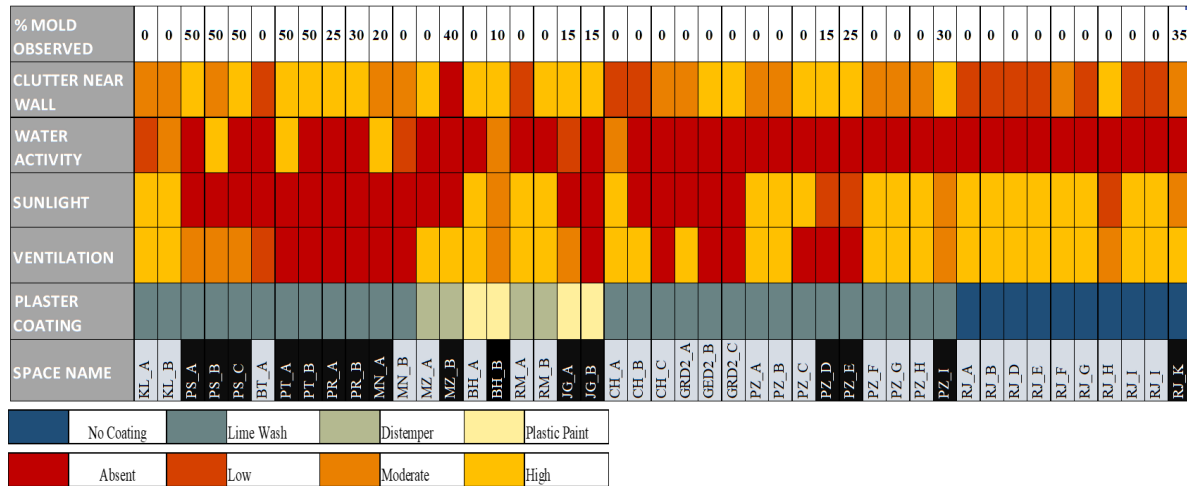


Figure 20 Space characteristics and mold growth relationship

The best and worst combination for predicting mold risk can be inferred from Figure XYZ. For example, the worst-case scenario was observed in spaces PT_B and PT_A. More than 50% of the walls were densely covered with mold. PT_B has a good scope of ventilation, but the openings were always closed. So, it can be marked as less ventilated, with no sunlight, no water activity, moderate storage near walls, and a limewash coating on the wall. Even though there was no water activity, other factors were dominating. The PT_A space was characterized by closed openings, no sunlight, high water activity, moderate storage near the walls, and lime wash. In both cases, it was observed that due to lack of ventilation and no sunlight the moisture was trapped inside the space which led to mold growth. The best combination is where lime plaster is not coated or coated with limewash, and the spaces were well ventilated and sunlit. The surveys suggest that mold growth in lime plaster was observed if the moisture transfer is obstructed. Therefore, if lime-plastered surfaces are allowed to breathe in ventilated spaces mold growth can be avoided.

Out of all the 45 spaces, 57% were spaces in Poles and 43% were individual residences. In comparison to the Pole houses, the individual residences had better strategies such as air vents, daylight spaces, and periodic maintenance. In the hotter month of March, they show better hygrothermal performance and were comfortable for more than 90% of the time. The indoors were cooler than the outdoor by 1 °C to 5 °C. The walls were drier and were recorded to be mostly below 0.5% of moisture content. The exposed lime plaster helped in moderating the indoor RH levels. The major issue observed in lime-plastered Pole houses was the lack of proper ventilation, sunlight, and maintenance.

3.2.5 Mold observation under the microscope

Samples were collected from the site to verify the presence of mold on the walls. The most common type of mold that is formed over lime plaster was observed. Figure 21 shows the collected samples as observed under a 40x simple microscope. In Figure 21a and Figure 21b, the tread-like filaments are the hyphae of the mold structure. The small granules are likely to be spores. Figure 21c and Figure 21d, show a sample scrapped from a gap between a wooden door frame and a lime plaster wall. This type of mold is different from the one observed on the walls having lime plaster. Observation under a high-resolution compound microscope will be required to identify the type of mold.

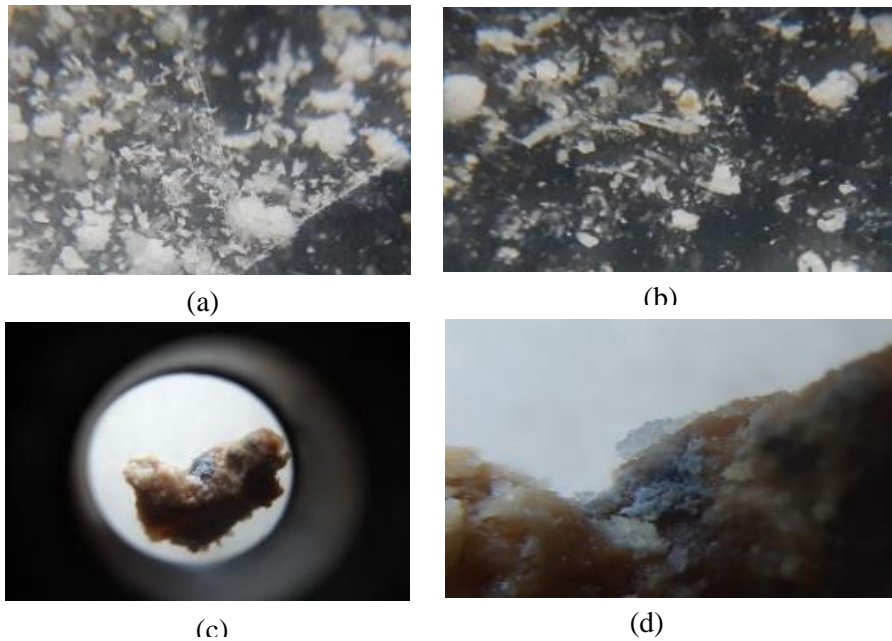


Figure 21 Mold sample under the 40x simple microscope

3.2.6 Studying the onset of mold growth on lime plaster samples

All the samples of lime plaster weighed 20 grams and had an initial moisture content of 0.6 %. Of the four containers, the one containing potassium sulphate (96 % RH) had early signs of mold growth. The other three containers (having RH of 75%, 80%, and 86%) showed no visible mold growth until the third week. However, at 96% RH mold growth was visibly seen on the lime plaster sample within three weeks (see Figure 22). Thus, a favourable environment for mold growth is created if the surface relative humidity in the space is more than 90%.



Figure 22 Mold growth observed under 96% relative humidity

4 Conclusion

In this work, the hygrothermal performance of lime plaster in naturally ventilated spaces is studied and co-related with mold risk. The survey of the lime-plastered spaces was carried out between December 2019 to March 2020. In relatively dry weather conditions, surface RH levels of the studied spaces were higher than the outdoor RH. The indoor RH levels are expected to rise further in the wet monsoon period and therefore prone to mold growth. The mold growth wasn't observed in spaces that were well maintained (uncluttered), well-ventilated and sunlit. Non-porous coatings on plastered surfaces led to

mold growth. Thus, it is important to maintain a breathable wall assembly and adequate ventilation to facilitate moisture transfer across the building envelope. Spaces finished with a lime wash and exposed lime plaster also showed lower indoor MRT than spaces with non-porous coatings.

Hygrothermal simulations with the EMPD model were able to capture moisture buffering in different materials. Hygrothermal simulations of some surveyed houses showed that the EMPD model can be employed to predict the duration for which the walls are exposed to high RH levels. Thus, mold growth risk on different wall surfaces can be identified. However, more numerical analysis with hygrothermal properties of typical lime plaster used in India needs to be carried out for realistic predictions. Walls with high surface RH were susceptible to mold risk if exposed to indoor RH levels greater than 60 % for more than four weeks. Experiments with lime plaster samples showed visible mold growth in 3 weeks under an environment with a relative humidity of around 95 %. By combining the above observation with the simulations, the chances of mold growth in a space can be predicted. The performance gap between a simulation and an actual case can also be narrowed down for better predictions if the simulations are carried out in collaboration with survey observations.

Overall, lime plaster is a sustainable and low embodied energy material with good moisture buffering capacity. It can moderate indoor RH levels and lead to lower MRT. Although it is prone to mold growth in high humidity conditions, avoiding non-porous coatings and maintaining adequate ventilation can reduce mold risk. Especially suited for historic buildings, lime plaster should also be considered in contemporary building practices.

4.1 Future Scope of work and recommendation and limitations

- Hygrothermal properties of typical lime plaster need to be derived.
- The composition of lime plaster used in pol houses is not known and cannot be easily derived as it is older than 300 years. An EDX spectra analysis is required to be done for the chemical signatures, yielding a general stoichiometric formula to know the possible compounds within the sample.
- The study should be carried out over a period of the year including the monsoon period with higher humidity.
- To improve the technical properties of lime plaster, optional additives (44)(19) (45) other than organic compounds should be explored. This could prevent the degradation and damage to the plaster.
- Observation and identification of mold under a compound microscope should be carried out.

5 Funding and Acknowledgement statement

The authors are grateful to Dr. Rajan Rawal and the Center for Advanced Research in Building Science & Energy of CEPT University for providing the loggers and instruments required to conduct the surveys. The authors would also like to thank Ms. Parul Zaveri and residents of the Pol houses for collaborating in providing access to residences in Ahmedabad.

6 Declarations and conflicts of interest

6.1 Conflicts of Interest

All authors declare no possible conflicts of interest.

6.2 Research ethics statement

Ethics approval is not needed.

6.3 Consent for publication statement

Authors have secured informed consent to participate in the study and to publication before submitting it to the journal

6.4 Open data and materials availability

No further data was used in addition to referenced works.

6.5 Authorship contribution

Rashmin Damle has been the guiding faculty in this study and Vismaya Paralkar has carried out data compilation, assessments, and reporting.

7 References

1. Doctor-pingel M, Vardhan V, et al. Use of Lime Mortar and Post-Occupancy Thermal Performance Analysis of Buildings [Internet]. Encyclopedia of Renewable and Sustainable Materials. Elsevier Inc; 2019. Available from: <http://dx.doi.org/10.1016/B978-0-12-803581-8.11308-6>
2. Osanyintola OF, Simonson CJ. Moisture buffering capacity of hygroscopic building materials: Experimental facilities and energy impact. *Energy Build.* 2006;38(10):1270–82.
3. Woloszyn M, Rode C. Tools for Performance Simulation of Heat , Air and Moisture Conditions of Whole Buildings Tools for Performance Simulation of Heat , Air and Moisture Conditions of Whole Buildings. 2008;(November 2014).
4. Zhang M, Qin M, Rode C, Chen Z. Moisture buffering phenomenon and its impact on building energy consumption. *Appl Therm Eng [Internet]*. 2017;124:337–45. Available from: <http://dx.doi.org/10.1016/j.applthermaleng.2017.05.173>
5. Gaur RC, Bansal NK. Effect of moisture transfer across building components on room temperature. *Build Environ.* 2002;37(1):11–7.
6. Ramachandra T V. Comparative analysis of greenhouse gas emissions from major cities of India. *Int J Renew Energy Environ Eng ISSN.* 2014;02(01):2348–157.
7. Lucas F, Adelard L, Garde F, et al. Study of moisture in buildings for hot humid climates. *Energy Build.* 2002;34(4):345–55.
8. Mendes N, Winkelmann FC, Lamberts R, Philippi PC. Moisture effects on conduction loads. *Energy Build.* 2003;35(7):631–44.
9. Arundel A V., Sterling EM, Biggin JH, et al., Sterling TD. Indirect health effects of relative humidity in indoor environments. *Environ Health Perspect.* 1986;VOL. 65(3):351–61.
10. Nielsen KF, Holm G, et al. Mould growth on building materials under low water activities . In uence of humidity and temperature on fungal growth and secondary metabolism. 2004;54:325–36.
11. Bornehag C, Sundell J. Dampness in Buildings and Health between Exposure to ““ Dampness ”” in Buildings and Health Effects. 2001;72–86.
12. Lstiburek. J. Moisture Control for New Residential Buildings | BSC [Internet]. ASHRAE J. 2009 [cited 2020 Feb 19]. Available from: <https://www.buildingscience.com/documents/digests/bsd-012-moisture-control-for-new-residential-buildings>
13. Singh M, Vinodh Kumar S, Waghmare SA. Characterization of 6-11th century A.D decorative lime plasters of rock cut caves of Ellora. *Constr Build Mater [Internet]*. 2015;98(December 2017):156–70. Available from: <http://dx.doi.org/10.1016/j.conbuildmat.2015.08.039>

14. Karanth R V., Krishnan K, Hegde KTM. Petrography of ancient Indian lime plaster. *J Archaeol Sci.* 1986;13(6):543–51.
15. Ravi R, Thirumalini S et al. Analysis of ancient lime plasters – Reason behind longevity of the Monument Charminar, India a study. *J Build Eng* [Internet]. 2018;20:30–41. Available from: <https://doi.org/10.1016/j.jobe.2018.04.010>
16. Venkatarama Reddy B V., Jagadish KS. Embodied energy of common and alternative building materials and technologies. *Energy Build.* 2003;35(2):129–37.
17. Liuzzi S, Stefanizzi P. Experimental study on hygrothermal performances of indoor covering materials. *Int J Heat Technol.* 2016;34(Special Issue 2):S365–70.
18. Tittarelli F, Giosuè C, Mobili A, Ruello ML. Influence of binders and aggregates on VOCs adsorption and moisture buffering activity of mortars for indoor applications. *Cem Concr Compos* [Internet]. 2015;57:75–83. Available from: <http://dx.doi.org/10.1016/j.cemconcomp.2014.11.013>
19. Toniolo L, Paradisi A, Goidanich S, Pennati G. Mechanical behaviour of lime based mortars after surface consolidation. *Constr Build Mater* [Internet]. 2011;25(4):1553–9. Available from: <http://dx.doi.org/10.1016/j.conbuildmat.2010.08.010>
20. Roger Hunt, Suhr M. Lime in old buildings [Internet]. [cited 2020 Feb 3]. Available from: <http://www.greenspec.co.uk/building-design/lime/>
21. Apte MD. New Building Material- Freshly Ground Lime Instead of Cement [Internet]. [cited 2020 Feb 3]. Available from: <https://www.nbcw.com/tech-articles/concrete/570-new-building-material-freshly-ground-lime-instead-of-cement.html>
22. Sabri AAM, Suleiman MZ. Study of the Use of Lime Plaster on Heritage Buildings ' in Malaysia : A Case Study in George Town , Penang. 2014;5:1–6.
23. Mold P, Godbey R, LYON E V., Odaka Y, Seto H, Nakaoka H, et al. Limewash : Compatible Coverings for. *Indoor Built Environ* [Internet]. 2016;25(2):1–11. Available from: <http://dx.doi.org/10.1016/j.enconman.2010.10.010>
24. Kang SH, Lee SO, Hong SG, Kwon YH. Historical and scientific investigations into the use of hydraulic lime in Korea and preventive conservation of historic masonry structures. *Sustain.* 2019;11(19):1–16.
25. Bastien D, Winther-Gaasvig M. Influence of driving rain and vapour diffusion on the hygrothermal performance of a hygroscopic and permeable building envelope. *Energy.* 2018;164:288–97.
26. Karaglozls A, Ph D, Salonvaara M, Kumaran K. The effect of waterproof coating on hygrothermal performance of a high-rise wall structure. *Therm Perform Exter Envel Build.* 1995;(1993):391–8.
27. Elert K, Rodriguez-Navarro C, Pardo, et al. Lime mortars for the conservation of historic buildings. *Stud Conserv.* 2002;47(1):62–75.
28. Viitanen H. Improved Model to Predict Mold Growth in. *VTT Tech Res.* 2007;
29. Chen WJ, Claridge DE, Rohrs C, Liao J. Modeling to predict positive pressurization required to control mold growth from infiltration in buildings in a hot and humid climate. *Build Environ* [Internet]. 2016;104:102–13. Available from: <http://dx.doi.org/10.1016/j.buildenv.2016.05.001>
30. Singh M, Jain KK, Singh T. Some studies on the suitability of lime mortars based on ancient Indian formulations for restoration purposes. *Superf Dell Archit Le Finiture, Atti del Convegno di Stud Bressanone, Italy Sci ebeni Cult.* 1990;151–8.

31. Energy Plus. EnergyPlus 9.2 [Internet]. 2019 [cited 2020 Apr 12]. Available from: <https://bigladdersoftware.com/epx/docs/9-2/engineering-reference/index.html>
32. Gangwar G, Kaur P. Traditional Pol houses of ahmedabad: An overview. *Civ Eng Archit.* 2020;8(4):433–43.
33. Abhikram [Internet]. [cited 2020 Apr 10]. Available from: https://www.abhikram.com/projects_details.php?Code=90
34. Judkoff RD, Neymark J. The BESTEST Method for Evaluating and Diagnosing Building Energy Sftware. ACEE Summer Study Energy Effic Build [Internet]. 1998;175–92. Available from: <https://aceee.org/files/proceedings/1998/data/papers/0515.PDF%0Ahttps://www.aceee.org/files/proceedings/1998/data/papers/0515.PDF>
35. Woods J, Winkler J, Christensen D. Evaluation of the Effective Moisture Penetration Depth Model for Estimating Moisture Buffering in Buildings. *Contract.* 2013;303(January):275–3000.
36. Zemanová L, Pokorný J, et al. Properties of modified lime-based plasters for renewal of historical buildings exposed to accelerated carbonation test. *Mater Sci Forum.* 2017;909 MSF:286–90.
37. Tran Le AD, Maalouf C, et al. Transient hygrothermal behaviour of a hemp concrete building envelope. *Energy Build* [Internet]. 2010;42(10):1797–806. Available from: <http://dx.doi.org/10.1016/j.enbuild.2010.05.016>
38. Wan H, Xu X, Gao JJ, Li A. A Moisture Penetration Depth Model of Building Hygroscopic Material. *Procedia Eng* [Internet]. 2017;205:3235–42. Available from: <https://doi.org/10.1016/j.proeng.2017.10.299>
39. Kielsgaard K. Sorption isotherms A catalogue. 1986;
40. Quincot G, Azenha M, Barros J, et al. Use of salt solutions for assuring constant relative humidity conditions in contained environments. *Found Sci Technol.* 2011;33.
41. Stanke DA, Danks RA, Muller CO, Hedrick RL, Fisher FJ, Osborn JE, et al. ASHRAE STANDARD Ventilation for Acceptable Indoor Air Quality. 2007;2007.
42. Walikewitz N, Jänicke B, Langner M, et al. The difference between the mean radiant temperature and the air temperature within indoor environments: A case study during summer conditions. *Build Environ.* 2015;84:151–61.
43. Maschinen B, Investition A, Beschaffungen G, Ersatzbeschaffungen B, Mittelherkunft S. Testo 606 Instruction Manual.
44. Volfová P, Pavlíková M, Pernicová R, et al. Properties of lime plaster with hydrophobic admixture. *Mater Sci Forum.* 2015;824:27–32.
45. Peterková J, Zach J, Sedlmajer M. Development of advanced plasters for insulation and renovation of building constructions with regard to their hygrothermal behaviour. *Cem Concr Compos* [Internet]. 2018;92:47–55. Available from: <https://doi.org/10.1016/j.cemconcomp.2018.05.014>

8 Appendix

Table 3 Characteristics of studied spaces

SPACE NAME	WALL DETAILS	MOULD GROWTH OBSERVED	FUNCTION	COATING OVER PLASTER	Volume (cu.m)
KL_A	North and West Wall Exposed	No Visible Mould Growth	Living Area	Lime Wash	34.52
KL_B	South and West Wall Exposed	Outside exposed wall	Kitchen	Lime Wash	36.62
PS_A	North Wall Exposed	No Visible Mould Growth	Living Area	Lime Wash	69.01
PS_B	Open to sky	On 1 Common Wall	Kitchen	Lime Wash	120.06
PS_C	No Exposed Wall	On all Walls	Store Room	Lime Wash	21.09
BT_A	North Wall Exposed	No Visible Mould Growth	Bedroom	Lime Wash	
PT_A	South and West Wall Exposed	Inside and Outside all Walls	Common area	Lime Wash	33.68
PT_B	North Wall Exposed	On all Walls	Bedroom	Lime Wash	23.32
PR_A	East Wall Exposed	On all Walls	Store Room	Lime Wash	72.90
PR_B	No Exposed Wall	On all Walls	Store Room	Lime Wash	25.80
MN_A	South Wall Exposed	On Common Walls	Living Area	Lime Wash	
MN_B	North Wall Exposed	No Visible Mould Growth	Kitchen	Lime Wash	
MZ_A	East Wall Exposed but shaded	No Visible Mould Growth	Small scale industry activity	Distemper	28.92
MZ_B	No Exposed Wall	On Both the Walls	Passage	No Coating	7.51
BH_A	West Wall Exposed	On East Wall	Living Area	Plastic Paint	41.10
BH_B	North and West Wall Exposed	On East Wall	Kitchen	Plastic Paint	31.50
RM_A	East Wall Exposed	No Visible Mould Growth	Living Area	Distemper	39.30
RM_B	North Wall Exposed	No Visible Mould Growth	Bedroom	Distemper	32.10
JG_A	North and East Wall Exposed	On all Walls	Common area	Plastic Paint	72.00
JG_B	No Exposed Wall	On all Walls	Store Room	Plastic Paint	45.00
CH_A	North Wall Exposed	No Visible Mould Growth	Kitchen	Lime Wash	26.19
CH_B	No Exposed Wall	No Visible Mould Growth	Bedroom	Lime Wash	52.96
CH_C	No Exposed Wall	No Visible Mould Growth	Store Room	Lime Wash	6.28
GRD2_A	East Wall Exposed	No Visible Mould Growth	Dining Area	Lime Wash	37.92
GED2_H	West Wall Exposed	No Visible Mould Growth	Store Room	Lime Wash	18.79
GRD2_I	East Wall Exposed	No Visible Mould Growth	Store Room	Lime Wash	22.75
PZ_A	South and West Wall Exposed	No Visible Mould Growth	Living Area	Lime Wash	210.77
PZ_B	South and West Wall Exposed	No Visible Mould Growth	Bedroom	Lime Wash	44.21
PZ_C	South and West Wall Exposed	On Common Walls	Basement Store Room	Lime Wash	45.26
PZ_D	South and West Wall Exposed	No Visible Mould Growth	Basement Store Room	Lime Wash	110.52
PZ_E	South and West Wall Exposed	On 2 Common Walls	Basement Store Room	Lime Wash	94.33
PZ_F	South and West Wall Exposed	No Visible Mould Growth	Common area	Lime Wash	107.28
PZ_G	South and West Wall Exposed	No Visible Mould Growth	Bedroom	Lime Wash	49.50
PZ_H	South and West Wall Exposed	No Visible Mould Growth	Bedroom	Lime Wash	113.83
PZ_I	South and West Wall Exposed	On Exposed Walls	Terrace Common area	Lime Wash	
RJ_A	South and West Wall Exposed	No Visible Mould Growth	Living Area	No Coating	196.00
RJ_B	South and West Wall Exposed	No Visible Mould Growth	Dining Area	No Coating	126.60
RJ_D	South and West Wall Exposed	No Visible Mould Growth	Living Area	No Coating	189.00
RJ_E	South and West Wall Exposed	No Visible Mould Growth	Bedroom	No Coating	69.60
RJ_F	South and West Wall Exposed	No Visible Mould Growth	Store Room	No Coating	33.60
RJ_G	South and West Wall Exposed	No Visible Mould Growth	Store Room	No Coating	105.00
RJ_H	South and West Wall Exposed	No Visible Mould Growth	Store Room	No Coating	47.20
RJ_I	South and West Wall Exposed	No Visible Mould Growth	Living Area	No Coating	183.41
RJ_I	South and West Wall Exposed	No Visible Mould Growth	Entrance Lobby	No Coating	17.92
RJ_K	South and West Wall Exposed	Inside and Outside Exposed Walls	Living Area	No Coating	73.41